

Serveur Académique Lausannois SERVAL [serval.unil.ch](http://serval.unil.ch)

## Author Manuscript

Faculty of Biology and Medicine Publication

This paper has been peer-reviewed but does not include the final publisher proof-corrections or journal pagination.

Published in final edited form as:

**Title:** Factor XIII Cross-linked Hyaluronan Hydrogels for Cartilage Tissue Engineering

**Authors:** Nicolas Broguiere, Emma Cavalli, Gian M. Salzman, Lee Ann Applegate, and Marcy Zenobi-Wong

**Journal:** ACS Biomater. Sci. Eng.

**Year:** 2016

**DOI:** [10.1021/acsbiomaterials.6b00378](https://doi.org/10.1021/acsbiomaterials.6b00378)

In the absence of a copyright statement, users should assume that standard copyright protection applies, unless the article contains an explicit statement to the contrary. In case of doubt, contact the journal publisher to verify the copyright status of an article.

## Factor XIII Cross-linked Hyaluronan Hydrogels for Cartilage Tissue Engineering

Nicolas Broguiere, Emma Cavalli, Gian M. Salzmann, Lee Ann Applegate, and Marcy Zenobi-Wong

ACS Biomater. Sci. Eng., **Just Accepted Manuscript** • DOI: 10.1021/acsbomaterials.6b00378 • Publication Date (Web): 20 Oct 2016

Downloaded from <http://pubs.acs.org> on October 24, 2016

### Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

# Factor XIII Cross-linked Hyaluronan Hydrogels for Cartilage Tissue Engineering

*Nicolas Broguiere<sup>†1</sup>, Emma Cavalli<sup>†1</sup>, Gian M. Salzman<sup>2</sup>, Lee Ann Applegate<sup>3</sup>, Marcy Zenobi-  
Wong<sup>\*1</sup>*

† Equal contributions

## Corresponding Author

\*Email: marcy.zenobi@hest.ethz.ch. Address: HPL J20, Otto-Stern-Weg 7, 8093 Zürich

<sup>1</sup>ETH Zürich, Cartilage Engineering and Regeneration Laboratory, Switzerland

<sup>2</sup>Schulthess Klinik, Lengghalde 2, 8008 Zürich, Switzerland

<sup>3</sup>Department of Musculoskeletal Medicine, Regenerative Therapy Unit, University Hospital of  
Lausanne, Switzerland

Keywords: cartilage hyaluronan chondroprogenitors transglutaminase bioadhesive

In this study transglutaminase-crosslinked hyaluronan hydrogels (HA-TG) are investigated for their potential treating cartilage lesions. We show the hydrogels fulfill key requirements: they are simultaneously injectable, fast-gelling, biocompatible with encapsulated cells, mitogenic, chondroinductive, form-stable and strongly adhesive to native cartilage. Human

1  
2  
3 chondroprogenitors encapsulated in HA-TG gels simultaneously show good growth and  
4  
5 chondrogenesis. Strikingly, within soft gels (~1 kPa), chondroprogenitors proliferate and deposit  
6  
7 extracellular matrix to the extent that the hydrogels reach a modulus (~0.3 MPa) approaching  
8  
9 that of native cartilage (~1 MPa) within 3 weeks. The combination of such off-the-shelf human  
10  
11 chondroprogenitor cell line with HA-TG hydrogels lay the foundation for a cell-based treatment  
12  
13 for cartilage lesions which is based on a minimally invasive one-step procedure, with improved  
14  
15 reproducibility due to the defined cells, and with improved integration with the surrounding  
16  
17 tissue due to the new hydrogel chemistry.  
18  
19  
20  
21  
22  
23

## 24 **1. Introduction**

25  
26 Cartilage tissue has limited self-repair ability after injury or disease, which has prompted  
27  
28 intensive efforts to engineer cell-based methods to regenerate the tissue.<sup>1</sup> In particular, matrix  
29  
30 assisted autologous chondrocyte implantation (MACI) has been shown to be effective in  
31  
32 comparison to microfracture,<sup>2</sup> but significant limitations and costs associated with cell expansion  
33  
34 and two surgeries have prompted the search towards alternatives.<sup>3</sup> Single step procedures have  
35  
36 been applied as early as 1982, when Albrecht and colleagues used autologous particulate  
37  
38 cartilage pieces to treat articular joint surface defects.<sup>4</sup> This technique matured into a clinical  
39  
40 product in the early 2000's with the introduction of cartilage autograft implantation system  
41  
42 (CAIS) showing satisfying 2-year safety data.<sup>5</sup> Varying follow-up papers have shown general  
43  
44 feasibility of minced autologous and allogeneic living cartilage pieces, with Christensen  
45  
46 reporting 2-year data among a small collective of patients that have been treated with particulate  
47  
48 cartilage pieces fixed by fibrin glue.<sup>6</sup> Clinical and MRI data showed good patient satisfaction and  
49  
50 morphologically robust cartilage tissue formation.  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 Other approaches to further advance the treatment of cartilage lesions include development of  
4 injectable materials which can undergo in situ polymerization. GelrinC, based on polyethylene  
5 glycol (PEG) diacrylate and fibrinogen,<sup>7</sup> as well as the chitosan-based BS-Cargel are acellular  
6 products designed to enhance outcome of microfracture by providing a 3D environment for the  
7 repair cells.<sup>8</sup> Other injectable systems such as those based on albumin, hyaluronan (HA) and  
8 PEG (Novocart Inject<sup>9</sup>) are designed to be combined with autologous expanded chondrocytes. In  
9 addition the use of juvenile cartilage cells, considered immune-privileged and with great  
10 regenerative potential, has recently entered phase II clinical trials with promising results  
11 (RevaFlex<sup>TM</sup>). In each clinical setting, an injectable material which is adhesive, chondrogenic  
12 and mitogenic is desired.<sup>10</sup> We recently reported the synthesis of novel HA-based injectable  
13 hydrogels which use the specific transglutaminase (TG) activity of the activated blood  
14 coagulation factor XIII (FXIIIa) for crosslinking.<sup>11</sup> The improved biocompatibility, gelling  
15 kinetics and adhesion due to this cross-linking scheme<sup>12</sup> are particularly attractive for cell  
16 delivery in cartilage applications. Furthermore, HA is a prominent component of cartilage tissue  
17 and is involved in many biological interactions (such as aggrecan binding to form large  
18 aggregates important for load bearing<sup>13</sup>) and signaling (through receptors such as CD44). Our  
19 synthesis is additionally based on high molecular weight HA which has been documented as  
20 anti-angiogenic, anti-oxidant and anti-inflammatory.<sup>14</sup>


21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46 In this paper, the HA-TG hydrogel is combined with human chondroprogenitor cells (hCCs)  
47 which were isolated by outgrowth culture from a 14 week fetal ulnar epiphysis. These cells have  
48 previously been shown to exhibit great homogeneity in expansion with steady proliferative  
49 potential<sup>15</sup> and produce phenotypically stable cartilage resistant to vascularization and  
50 mineralization in an in vivo subcutaneous mouse model.<sup>16</sup> hCCs also have low immunogenicity  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 which makes them appropriate as an allogeneic off-the-shelf cell source where many patients can  
4  
5 be treated in single step procedures from the same cell line.  
6  
7

## 8 2. Results and discussion


### 9 2.1. Material synthesis

10  
11 To impart FXIIIa sensitivity to HA, we substituted the polysaccharide with a spacer followed by  
12  
13 peptides which are specifically recognized and covalently ligated by the enzyme. One of the  
14  
15 peptides donates the reactive lysine (TG/Lys) and the other the reactive glutamine (TG/Gln). HA  
16  
17 substituted with TG/Gln and TG/Lys are synthesized separately, and then combined in equimolar  
18  
19 amounts together with the enzyme to trigger the gelation, which can be done directly into  
20  
21 cartilage defects and with encapsulated cells, as illustrated in Figure 1. The HA starting material  
22  
23 as well as FXIII and thrombin are all in widespread use in the clinics, making it unlikely that any  
24  
25 of the gel derivatives could create an immune response.<sup>17</sup> The fast and mild gelation makes the  
26  
27 material particularly adapted to injection in situ, which would be optimum for clinical  
28  
29 translation. For example, the gelling time for 1% (w/v) gels with 10 U/ml FXIIIa is on the order  
30  
31 of ~30 s (time during which the precursor solution can be pipetted up and down after adding the  
32  
33 enzyme until it forms a gel strong enough to clog the pipette) and no side reactions occur which  
34  
35 could lead to toxicity due to the specificity of the enzyme.  
36  
37  
38  
39  
40  
41  
42  
43

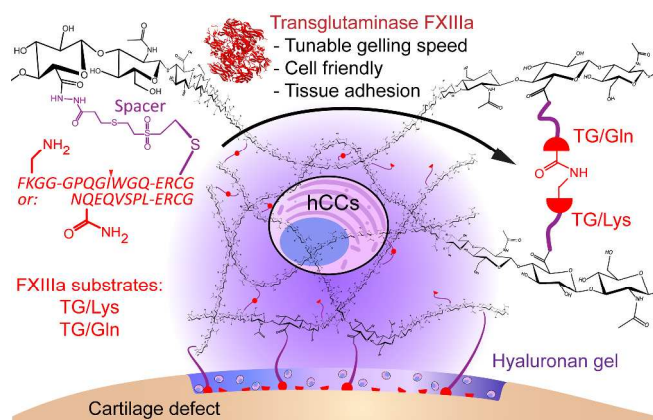

1  
2  
3 **Figure 1.** Concept schematics showing the gelation mechanism of transglutaminase (TG) cross-  
4 linked hyaluronan (HA). The lysine and glutamine residues that are covalently cross-linked by  
5 the TG FXIIIa are highlighted on the left, and the amide bond resulting from the conjugation is  
6 shown on the right. HA chains appear in black, peptides in red with reactive side chains  
7 explicitly shown, and the spacer/adaptor between the peptides and the HA is in purple.  
8 Encapsulated human chondroprogenitor cells (hCCs) and adhesion to cartilage tissue are also  
9 represented.  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19

20  
21 The synthesis of the HA-TG precursors has been described in detail previously.<sup>11</sup> In short, HA  
22 was first thiolated using EDC activation and hydrazide conjugation of a dithiol containing  
23 compound, followed by reduction of the dithiol with TCEP to yield HA-SH (Figure 2, Step 1).  
24 Then, a large excess of divinyl sulfone was added, to exchange the thiol functionality to vinyl  
25 sulfones (VS), yielding HA-VS. Finally, peptides containing a cysteine cassette were reacted  
26 onto the HA-VS, using again the efficiency of the Michael addition of thiols on VS (Figure 2,  
27 step 3). At every step, dialysis was the method of choice for removal of the buffers and unreacted  
28 small molecules, because it is very efficient with polymers and ensures no stress on the high MW  
29 HA chains, preserving the molecular weight.  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

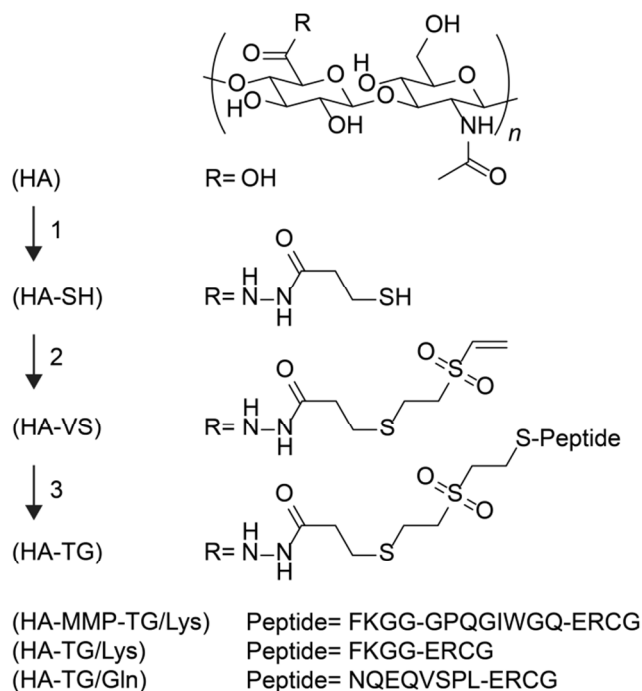

27  
28  
29  
30  
31  
32

**Figure 2.** Chemical synthesis of HA-TG precursors. Reaction conditions are 1/ EDC, MES pH4.1 to 4.5, DTPHY then TCEP, 2/ DVS, TEOA pH8, 3/ Peptide, TEOA pH8.

33  
34  
35  
36

To make gels with MMP sensitivity, we made a version of HA-TG that incorporated an MMP cleavable sequence within the TG/Lys peptide (Figure 2).

37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

In this procedure, we targeted (through the amount of reagents in the first step) a substitution rate of 10%, which was confirmed by proton NMR on the HA-VS in D<sub>2</sub>O as shown previously (VS peaks between 6 and 7 ppm versus acetylate peak from HA backbone at 1.9 ppm). Complete substitution of the HA-VS with peptides was confirmed by the complete disappearance of the VS peaks.

48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60


Since high molecular weight polymers and viscous solutions are difficult to analyze in details by NMR due to peak broadening, and since the HA-TG is an extreme case of such a solution, we treated the HA-TG precursor HA-TG/Lys with hyaluronidase at 10 U/ml overnight at 37°C to partially hydrolyze the polysaccharide backbone and get clear NMR spectra. Reference spectra



1  
2  
3 of unmodified HA, TG/Lys and DTPHY were used for peak identification, as well as previously  
4 published work on HA proton and carbon NMR.<sup>18</sup> To assign the peaks (especially on TG/Lys,  
5 for which no reference was known), the neighbours in the COSY spectrum together with  
6 multiplicity and integrals from the <sup>1</sup>H spectrum were used. HSQC spectrum helped to  
7 distinguish overlapping peaks and was used to assign the carbons in the <sup>13</sup>C spectrum. New  
8 peaks in the conjugate and cysteine beta-carbon shift show the creation of the linker and confirm  
9 the chemical structure (Supplementary Figures 7-10).  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21

## 22. **Mechanical characterization**

22  
23  
24 The gelling behavior was characterized by rheometry (Figure 3A-B). Instead of pre-activating  
25 FXIII with thrombin as was done in the PEG literature, we reasoned that in situ activation of  
26 FXIII would give more interesting gelling kinetics. This way, a quite high amount of FXIII can  
27 be used, for very fast equilibration after activation, and the initial gelling speed can be tuned with  
28 the amount of thrombin, to have the gelling onset at the desired time (this can be seen as a cross-  
29 linking method having second order kinetics versus time instead of the usual linear progression).  
30 It also means the same enzyme concentrations can be used for any macromer content, always  
31 yielding a similar gelation onset time. We chose to use 20 U/ml of FXIII and 12.5 U/ml of  
32 thrombin to obtain a gelation onset at around 1 min and an equilibration to a plateau after 10  
33 min. In comparison, typical PEG gels formed by Michael addition typically have an onset of >10  
34 min and equilibration in >1h at physiological pH.<sup>19</sup> The very high number of functional groups  
35 present on a single molecule, due to the high molecular weight of the HA precursor and 10%  
36 substitution rate, is expected to contribute largely to the fast gelation, together with the good  
37 kinetics of FXIIIa catalyzed cross-linking in general.  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

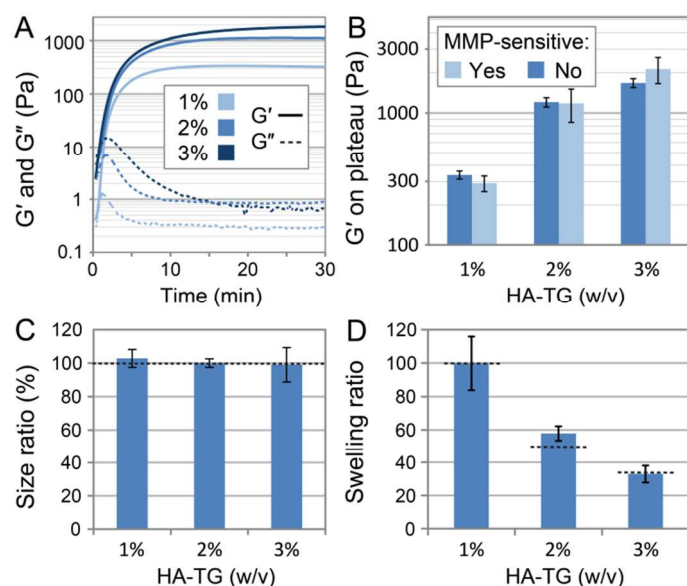

**Figure 3.** Material properties. (A) Representative gelling curves as monitored by rheometry showing the build-up of the storage  $G'$  and loss  $G''$  moduli for various concentrations of HA-TG. Note the fast gelation and equilibration to a plateau. (B) Values of the final storage modulus (taken at 30 min), showing the range of stiffness used in this study and the absence of influence from MMP sensitive sequence addition. (C) Change in diameter of the gels after 4 days of swelling in PBS. The dotted line indicates no change. (D) Swelling ratio (wet/dry weight of the gels) after 4 days of swelling in PBS. The dotted line indicates the values expected for no mass loss or volume change. Error bars: SD with  $n=8$  (for C and D at 3%) or  $n=3$  (the rest).


Macromer precursor solutions of 1 to 3% gave storage moduli ranging from  $\sim 0.3$  to 2 kPa, which span a range of stiffness that supported high cell viability.<sup>19</sup> Stable gels could still be formed down to at least 0.25% (w/v), but the high viscosity of the solutions at more than 3% makes the handling of more concentrated precursors difficult. There was no difference in mechanical properties of the HA-TG gel due to inclusion of the MMP-sensitive peptide.

1  
2  
3 Complete degradation of the gels could be achieved by treating them with either 10 U/ml  
4 hyaluronidase in PBS overnight at 37°C, or 0.25% trypsin for 15 min at 37°C. This indicates  
5 biodegradation is not hindered by TG cross-linking. The cells were nevertheless stable when  
6 used for cell cultures, as shown in the following sections.  
7  
8  
9  
10  
11

12 Measurement of gel diameter and swelling ratios (dry mass over wet mass) showed that the  
13 gels did not undergo any dimensional change or polymer loss compared to D0 cast gels after  
14 incubation in PBS for 4 days (Figure 3C-D). The stable polymer content over 4 days  
15 demonstrates that essentially all HA chains were cross-linked, something which was expected for  
16 such a high number of functional groups per polymer chain. The lack of swelling or shrinkage,  
17 however, was a remarkable finding as it indicates a perfect balance of attraction and repulsion  
18 between the chains which allowed the gels to maintain their size at each concentration examined.  
19 Every part of the polymer chain likely plays a role in the auspicious shape stability, with  
20 negative charge on the HA contributing repulsion, peptides contributing positive charges, and the  
21 spacers hydrophobicity. As a partial confirmation of this reasoning, we measured the change in  
22 the diameter of HA-TG 1% gel disks when the ionic strength of the buffer is altered, which  
23 essentially changes the extent of shielding of the negative charge on the chains (Supplementary  
24 Figure 4). As expected, gels immersed in ultrapure water increased in size while gels immersed  
25 in brine were shrinking (by approximately 200% and 10% respectively). The shape stability of  
26 HA-TG in physiological conditions is in contrast to most hydrogel systems where chain-chain  
27 and chain-solvent interactions lead to significant gel shrinkage or swelling. In these cases the  
28 unpredictable concentration- and time-dependent shape change can cause tissue engineered  
29 constructs to delaminate or pop out from their site of implantation.  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54

### 55 **2.3. Adhesion to cartilage explants**

56  
57  
58  
59  
60

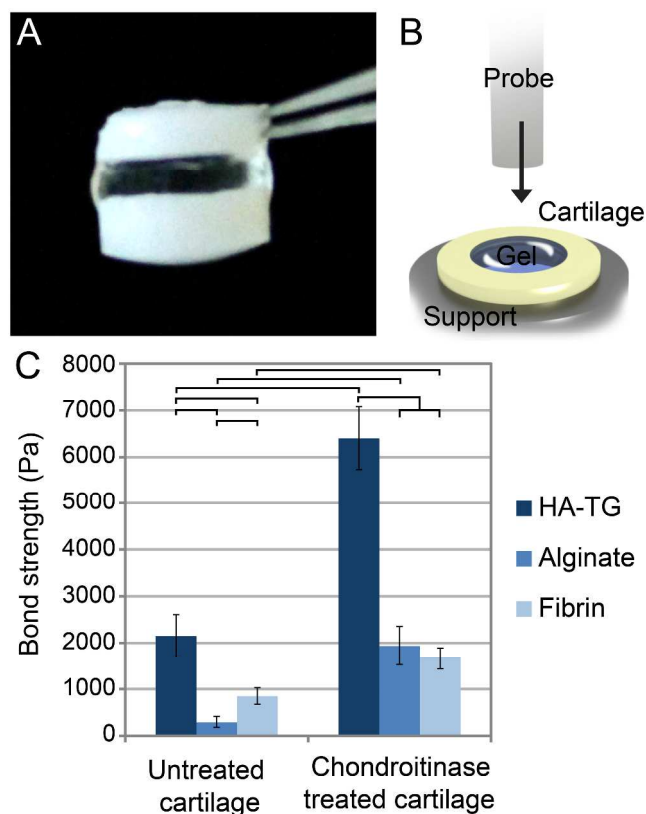

**Figure 4.** Adhesion to cartilage. (A) Cartilage biopsies adhered together with a gel layer. (B) Setup of the push-out assay for bond strength determination. (C) Bond strength of HA-TG gels compared with alginate and fibrin. Brackets:  $p < 0.05$ . Error bars: SEM  $n=6$ .

Adhesion to cartilage explants was studied with push-out tests of cylinders of gels made in 4 mm rings of bovine cartilage (Figure 4). The adhesion was compared to fibrin, a common surgical glue and sealant,<sup>20</sup> and alginate, which is the most common hydrogel for 3D chondrocyte culture but is not adhesive.<sup>21</sup> The HA-TG was found to be significantly more adhesive to cartilage than fibrin glue, which was itself more adhesive than alginate (student  $t$ -tests  $p < 0.05$ ). When the cartilage surface was treated with chondroitinase, to remove the polysaccharides and expose the protein part of the cartilage matrix, which is what mediates the adhesion in all three cases, the adhesion strength was found to be increased by approximately 2,


1  
2  
3 3, and 6 fold for fibrin, HA-TG, and alginate respectively. Alginate and fibrin were becoming  
4  
5 comparable, but HA-TG adhesion was ~3 times stronger than the controls, reaching a bond  
6  
7 strength of more than 6 kPa.  
8  
9

#### 10 11 12 **2.4. Cartilage formation from encapsulated hCCs** 13

14  
15 Finally, hCCs were encapsulated in the hydrogels to study their potential to support  
16  
17 chondrogenesis and effective cartilage tissue formation. These cells are particularly appealing for  
18  
19 clinical translation due to their high chondrogenic potential and ability to treat many patients in a  
20  
21 reproducible manner. They do not constitutively express cell surface molecules required for  
22  
23 induction of T cell immune responses, and they were shown not to stimulate allogeneic T cells in  
24  
25 *vitro*.<sup>22</sup> We analyzed the biological and mechanical outcome of hCCs in HA-TG cultures at 3  
26  
27 weeks post-encapsulation (D21). Alginate gels were used as controls.  
28  
29

30  
31 Live/dead assays showed nearly full viability in all conditions (Figure 5A), and cell  
32  
33 morphology as seen from calcein (whole cell) and actin staining (Figure 5B) was strongly  
34  
35 dependent on polymer concentration. Cells spread and proliferated to fill almost the whole space  
36  
37 in the softest gels, whereas they only formed small clusters without spreading in the stronger  
38  
39 gels. Confocal imaging of fluorescein tagged HA-TG gels (Supplementary Figure 5) showed that  
40  
41 the pore size was under the resolution limit (~200 nm) in all conditions. The differences in cell  
42  
43 spreading are therefore not directly explained by gel porosity, and have to involve gel  
44  
45 deformation or degradation. Second harmonic generation (SHG) at 60 micron depth from the  
46  
47 surface was collected simultaneously with calcein/PI fluorescence. This provided a way to check  
48  
49 overall collagen production in a non-type-specific way directly amongst the living cells. The soft  
50  
51 gels clearly stood out from the rest for being completely filled with a dense collagen network,  
52  
53 whereas the other conditions just showed collagen deposition pericellularly. The collagen  
54  
55  
56  
57  
58  
59  
60


1  
2  
3 appeared fibrillar on the very surface of the gel, which is commonly seen from collagen 1  
4 staining of such engineered cartilage constructs, but more homogeneous inside the gel, though it  
5  
6 staining of such engineered cartilage constructs, but more homogeneous inside the gel, though it  
7  
8 is deposited in the shape of the spread cells.  
9

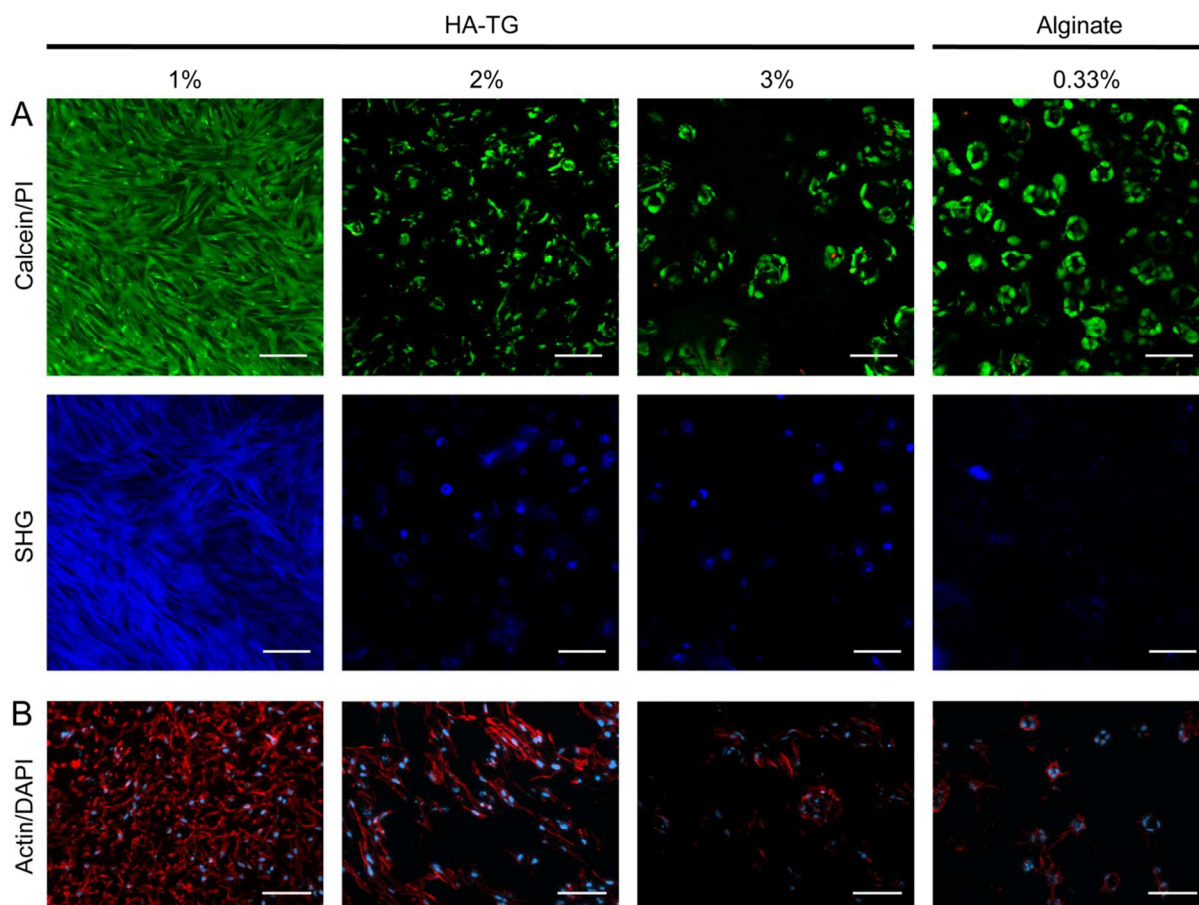

41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

**Figure 5.** Cell and collagen morphology visualized with non-specific markers. (A) Multiphoton live imaging, with simultaneous acquisition of calcein (cytoplasm of live cells, green), propidium iodide (PI, nuclei of dead cells, red), and second harmonic generation (SHG, assembled collagen, blue). All conditions are highly viable, while cells spread, proliferate, and deposit a dense collagen matrix in soft HA-TG gels only. Images are acquired at  $\sim 60 \mu\text{m}$  depth beneath the surface of the gels. (B) Actin cytoskeleton (phalloidin, red) and nuclei (DAPI, blue) imaged in the center of the gels from fixed cryosections. This highlights that the spreading and proliferation

of hCCs in soft HA-TG gels are not merely surface effects. (A+B) Images are at 21 days post encapsulation. Scale bars: 80  $\mu$ m.

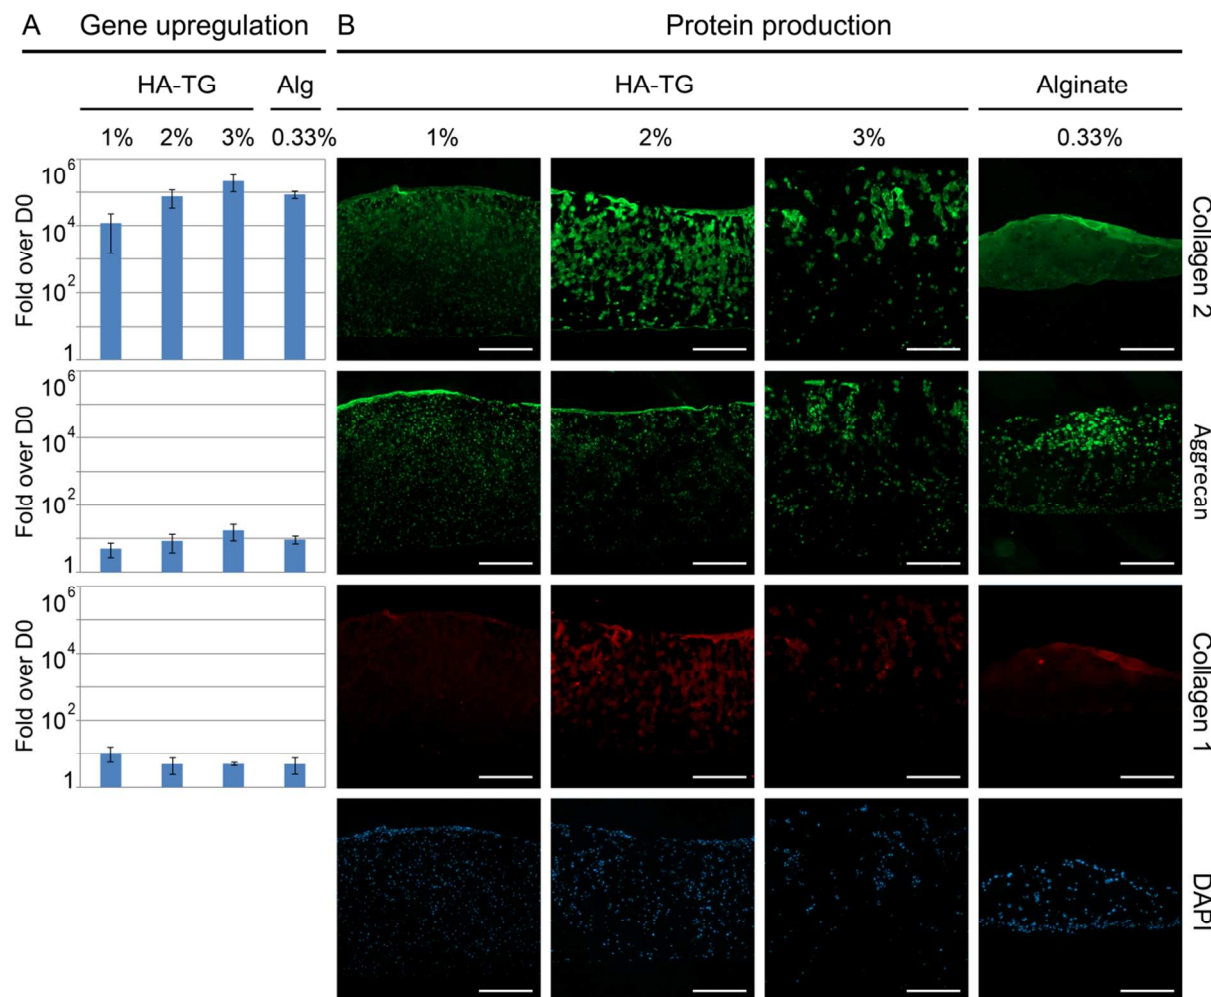

**Figure 6.** Cartilage production by encapsulated hCCs as seen from (A) gene expression 21 days post encapsulation, normalized to expression on the day of encapsulation (D0), and (B) matrix protein deposition. Each image is from a vertical slice of the gel taken from the center of the cylinder. Collagen 1, collagen 2 and DAPI are acquired on the same section. Scale bars: 400  $\mu$ m.

We then investigated the matrix deposition at the gene and protein level with qPCR normalized to D0 and immunofluorescence, respectively (Figure 6). In all conditions, collagen 2 gene


1  
2  
3 expression increased at least  $10^4$  fold, whereas collagen 1 upregulation was less than 10 fold,  
4  
5 indicating good induction of chondrogenesis in all conditions. The high collagen 2 expression  
6  
7 was also translated to the protein level: the soft gels were entirely filled with collagen 2 matrix,  
8  
9 whereas the stiffer gels had only thin and more compact collagen 2 deposition around the cell  
10  
11 clusters, reminiscent of what was seen in SHG. The collagen 2 / collagen 1 ratio was slightly  
12  
13 higher in stiffer gels, which was expected as these cells had a rounder cell morphology.<sup>23</sup>  
14  
15 Aggrecan was upregulated on the order of 10 fold in all conditions, again with higher expression  
16  
17 in the stiffer gels. Aggrecan deposition was particularly strong on the HA gels surface. The most  
18  
19 striking difference between the conditions is that the matrix deposition is more pericellular in  
20  
21 stiffer gels and more homogeneous in softer gels.  
22  
23  
24  
25  
26

27 The pattern of protein deposition was strongly depth-dependent, which can be attributed to that  
28  
29 fact that the hydrogels were cultured in cylindrical PDMS casters bound to coverslips. The  
30  
31 stainings clearly show proximity to the surface strongly benefits protein production, probably  
32  
33 due to better access to nutrients/growth factors.  
34  
35

36 Finally, the most important outcome for clinical applications, the evolution of the mechanical  
37  
38 properties over time, was evaluated (Figure 7). While it was found that stiff 3% gels essentially  
39  
40 maintain their stiffness over the 3 week culture period, soft 1% gels showed a tremendous  
41  
42 increase in stiffness from an initial compressive modulus of  $\sim 1$  kPa to a final value close to 0.3  
43  
44 MPa. Native cartilage measured in the same conditions was found to be  $\sim 1$  MPa, consistent with  
45  
46 reported literature values.<sup>24</sup> It is particularly noteworthy that the stiffness of the soft gels reached  
47  
48 the order of magnitude of native cartilage in a clinically-relevant time frame. Intermediate 2%  
49  
50 gels had values between these two extremes, and alginate gels were too unstable to be measured  
51  
52 at D0 and only reached 10 kPa at D21. It is important to note that while the alginate gels  
53  
54  
55  
56  
57  
58  
59  
60



underwent significant shrinkage and shape change, all of the HA-TG gels had nearly perfectly stable shape and size over the culture time. These stiffness results strongly correlate with the collagen deposition as seen by SHG that only shows assembled matrix, whereas gene expression was not the best predictor of physical outcome.

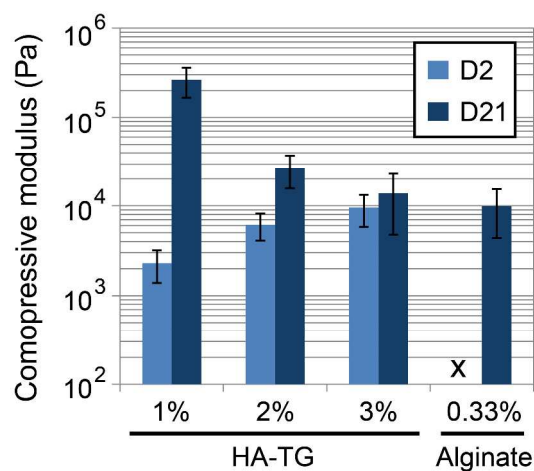

**Figure 7.** Evolution of the mechanical properties with matrix deposition by the hCCs between 2 and 21 days after encapsulation. Bovine hyaline cartilage was found to have a compressive modulus of  $10^6$  Pa in the same measuring conditions. Error bars: SD from  $n=3$  (D2) and  $n=6$  (D21).

All the cell experiments were performed as well with MMP sensitive HA-TG gels, and none of the characterizations showed a significant difference between MMP sensitive and insensitive gels (data shown in Supplementary Figures 1-3). These results suggest that the increased cost and risk of premature gel degradation when using MMP sequences is not warranted, and that the use of HA-TG without MMP sequences is the best choice for cartilage tissue engineering.

Other HA based hydrogels have been described, such as those cross-linked with tyramines/HRP/hydrogen peroxide<sup>25</sup>, methacrylates<sup>26</sup>, aldehydes, thiols, and Huisgen cycloaddition, and have been reviewed<sup>27</sup>. In particular, photo-crosslinked HA hydrogels were

1  
2  
3 shown to support chondrocyte matrix deposition and chondrogenic differentiation of  
4  
5 mesenchymal stem cells (MSCs) both in vitro and in vivo. In direct comparison to relatively inert  
6  
7 poly(ethylene glycol) (PEG) hydrogels, with matched stiffness and same cross-linking chemistry,  
8  
9 HA supported enhanced expression of cartilage-specific markers. The gene expression and  
10  
11 matrix deposition found in methacrylated HA was close to what we obtain with  
12  
13 chondroprogenitors in stiff HA-TG gels, however the authors did not investigate softer  
14  
15 hydrogels, which give better results in our case, or the stiffening of the gels overtime due to  
16  
17 matrix deposition.<sup>26</sup> Also, all of those cross-linking schemes have at least one drawback  
18  
19 compared to the one presented here, in terms of specificity/toxicity, of gelling kinetics, of  
20  
21 stability of the precursors in particular when working with high molecular weight HA, of  
22  
23 adhesion to cartilage, or of ease of handling and injectability. Other enzymatically cross-linked  
24  
25 hydrogels have been described as well<sup>28</sup> some of them enabling fast gel formation, low toxicity  
26  
27 and adhesion to cartilage, but the amount of matrix deposition and the resulting gel stiffening  
28  
29 observed in our system are still outstanding. For example, some recent work was published  
30  
31 showing chondrocyte encapsulation in injectable carboxymethylated pullulan-chondroitin sulfate  
32  
33 hydrogels. Fast gelling and good cell viability were demonstrated, but collagen 2 upregulation  
34  
35 compared to 2D cultures, cartilage, or any other reference was not shown, collagen 2 deposition  
36  
37 was only pericellular, and no gel stiffening resulting from matrix deposition was reported.<sup>29</sup>  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

### 48 **3. Conclusion**

49  
50 We investigated the use of HA derivatives that can be cross-linked with the transglutaminase  
51  
52 activity of FXIIIa for cartilage tissue engineering. We showed these gels have an ideal set of  
53  
54 properties for treating cartilage lesions: they are injectable, very fast gelling, adhesive to  
55  
56  
57  
58  
59  
60

1  
2  
3 cartilage tissue, retain their shape and have excellent biocompatibility. Human  
4  
5 chondroprogenitors encapsulated in the gels showed tunable proliferation and good cartilage  
6  
7 matrix deposition, transforming the gels into cartilage-like tissue within three weeks. Strikingly,  
8  
9 the softest 1% gels showed a tremendous increase in stiffness over the culture time, reaching a  
10  
11 stiffness of the same order of magnitude as native cartilage. The material development and in  
12  
13 vitro characterization presented here support that HA-TG has potential for clinical translation,  
14  
15 which would provide a 1-step treatment simpler than current standards, and should be brought  
16  
17 forward to in vivo evaluation.  
18  
19  
20  
21  
22  
23  
24

#### 25 **4. Experimental Section**

26  
27 All chemicals were purchased from Sigma-Aldrich and cell culture reagents from  
28  
29 ThermoFisher Scientific unless stated otherwise.  
30

31  
32 HA-SH synthesis: 400 mg (1 mmol of the disaccharide repeat unit) of HA sodium salt  
33  
34 (Lifecore Biomedical, 1.01-1.8 MDa), and 23.8 mg (0.1 mmol) of 3,3'-dithiobis(propanoic  
35  
36 dihydrazide) (DTPHY, Frontier Scientific) were dissolved in a 150 mM MES solution with  
37  
38 occasional gentle swirling (final pH 4.1). Then 38.4 mg (0.2 mmol) of 1-ethyl-3-(3-  
39  
40 dimethylaminopropyl)carbodiimide (EDC, Fluka) was dissolved in 1 ml of deionized water and  
41  
42 added dropwise with stirring. The stirring was stopped and the reaction was allowed to continue  
43  
44 overnight. The pH increased towards ~4.5 during the course of the reaction, with MES buffer  
45  
46 preventing it from going higher. Then, 143.33 mg (0.5 mmol) of TCEP-HCl (Fluorochem) was  
47  
48 dissolved in 500  $\mu$ l water and added, the solution was homogenized by swirling, and the  
49  
50 reduction was left to proceed overnight in a standing sealed flask. Finally, 1 g (17 mmol) of  
51  
52 NaCl was added to the solution, and the mixture was dialyzed against ultrapure water balanced to  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 pH 4.5 with dilute HCl, with 4 water changes over 24h, to yield a solution of pure HA-SH  
4  
5 sodium salt.  
6

7  
8 *HA-VS synthesis:* The HA-SH solution recovered from the previous dialysis was added  
9  
10 dropwise into a solution of 1 ml (10 mmol) divinyl sulfone (DVS) in 40 ml of triethanolamine  
11  
12 (TEOA) buffer, 300 mM, pH 8.0. The reaction was left to proceed for 2h at RT, then 1 g of NaCl  
13  
14 was added and the solution was dialyzed against ultrapure water to yield pure vinyl sulfone-  
15  
16 substituted HA (HA-VS). The substitution rate was measured by comparing the peaks at 6.75  
17  
18 ppm (vinyl sulfones) and 1.75 ppm (N-acetyls from HA) from proton NMR in D<sub>2</sub>O and found to  
19  
20 be 10% of the carboxylic acids on HA.  
21  
22  
23

24  
25 *HA-TG/Lys and HA-TG/Gln:* The HA-VS was split in two equal parts. One half was  
26  
27 substituted with a FXIIIa substrate peptide that provides a reactive glutamine residue (TG/Gln:  
28  
29 NQEQVSPL-ERCG) and the other half with the peptide providing the reactive lysine (TG/Lys:  
30  
31 FKGG -ERCG). For a matrix metallo-proteinase (MMP) sensitive version of the gels, a lysine  
32  
33 donor with an MMP-sensitive sequence <sup>30</sup> was used instead (MMP-TG/Lys: FKGG-  
34  
35 GPQGIWGQ-ERCG). Peptides (Anawa) contained ~40% salt which was taken into account in  
36  
37 the molarity calculations. For conjugation, 10 ml of TEOA buffer 300 mM, pH 8.0 was added to  
38  
39 each HA-VS portion, the solutions were deoxygenated by bubbling with nitrogen gas, and finally  
40  
41 the peptides were added at 1.3 excess over the VS. The solutions were quickly homogenized, the  
42  
43 flasks sealed, and the reactions left to proceed overnight without stirring. Finally, 2 g of NaCl  
44  
45 were dissolved in each flask, and the products were dialyzed against ultrapure water. The  
46  
47 resulting pure HA-TG components were sterilized by 0.4 μm filtration, aliquoted, and  
48  
49 lyophilized under sterile conditions. NMR spectra were acquired on a Bruker 600 Mhz  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 instrument, using 15 to 25 mg of compound in 0.6 ml deuterated water, and spectra were  
4  
5 analyzed using MestReNova.  
6

7  
8 *HA-TG gel formation:* Aliquots of HA-TG/Lys and HA-TG/Gln were resuspended at 1, 2, or  
9  
10 3% (w/v) in sterile filtered TBS (NaCl 150mM, CaCl<sub>2</sub> 50 mM, TRIS 50 mM, balanced to pH  
11  
12 7.6). Then, the two solutions were combined in equal volume to form HA-TG polymer stock. To  
13  
14 trigger the gelation of 60  $\mu$ l of HA-TG solution, 1.5  $\mu$ l of thrombin solution (Baxter, 500 U/ml)  
15  
16 followed by 6  $\mu$ l of FXIII solution (Fibrogammin, CSL Behring, 200 U/ml) were added. Gelation  
17  
18 occurred in  $\sim$ 1 min, which left enough time to transfer the liquid precursor.  
19  
20

21  
22 *Alginate gel formation:* Alginate (Novamatrix) at 0.33% (w/v) (matching the stiffness of 3%  
23  
24 HA-TG gels) in NaCl 150mM was placed in 4 mm diameter – 1 mm height cylindrical PDMS  
25  
26 casters on coverslips, and gelled in  $\sim$ 500  $\mu$ l of 100 mM CaCl<sub>2</sub> solution for 1h, diffused through  
27  
28 a pre-wetted membrane. The membrane and calcium were then removed and the gel covered  
29  
30 with culture medium.  
31  
32

33  
34 *Shear moduli measurements:* After adding the FXIII and thrombin, the gel precursor was  
35  
36 quickly loaded onto an Anton Paar MCR 301 rheometer equipped with a 20 mm plate-plate  
37  
38 geometry and metal floor, pre-warmed to 37°C and with humidified chamber. The probe was  
39  
40 quickly lowered to measuring position (0.1 to 0.2 mm, monitoring the gel precursor forming a  
41  
42 ring around the geometry while lowering the probe to ensure the measuring space is precisely  
43  
44 filled). The gelation was then monitored at 1 Hz with 4% strain, which was within the linear  
45  
46 viscoelastic range of the gels (Supplementary Figure 6).  
47  
48

49  
50 *Compressive modulus measurements:* Gels were left to swell for at least 2 days in PBS and  
51  
52 tested under unconfined compression using a TA.XTplus Texture Analyzer (Stable  
53  
54 Microsystems) with a 500 g load cell. The samples were compressed to a final strain of 10% at a  
55  
56  
57  
58  
59  
60

1  
2  
3 rate of 0.01 mm/s. The compressive modulus E reported is the slope of the initial linear range of  
4  
5 the stress-strain curve.  
6  
7

8 *Adhesion strength measurements:* Bovine articular cartilage samples with 1-2 mm thickness  
9  
10 were harvested from the knee joints of calves aged 3-6 months. Cartilage rings of 8 mm in outer  
11  
12 diameter and 4 mm inner diameter were prepared using biopsy punches and washed in PBS. The  
13  
14 explants were then randomly divided in two groups: one group was left in PBS while the other  
15  
16 was incubated for 15 minutes at 37°C in 1 U/ml chondroitinase ABC followed by 3 washes with  
17  
18 PBS. The chondroitinase digestion results in approximately 50  $\mu$ m digestion of GAGs as  
19  
20 confirmed by Alcian blue staining (data not shown). Gels were injected into the circular hold of  
21  
22 the cartilage explants and left to gel for 20 minutes at 37°C in a humidified chamber. To prevent  
23  
24 leakage the explants were laid on a parafilm-coated surface. HA-TG gels were made as described  
25  
26 at 3% (w/v), alginate gels at 1.5% (w/v) and gelled by immersion for 1h in a 100 mM calcium  
27  
28 chloride solution, and fibrin gels contained 2% (w/v) fibrinogen and were gelled with 1 U/ml of  
29  
30 thrombin for 1h at 37°C. Push-out tests were performed at 0.5 mm/s rate with a 3 mm rod. The  
31  
32 bond strength was calculated as the maximum force divided by the area of the inner punched  
33  
34 hole.  
35  
36  
37  
38  
39

40  
41 *hCCs isolation and expansion protocol:* hCCs were harvested and isolated as described by  
42  
43 Darwiche et al. Briefly, a tissue biopsy from the proximal ulnar epiphysis of a 14-week gestation  
44  
45 donor was taken and minced. hCCs grew out of the tissue pieces. Cells were cultured for up to 2  
46  
47 weeks in DMEM (cat. 41966) containing 10% v/v FBS, 2mM L-glutamine, and 10  $\mu$ g/ml  
48  
49 Gentamycin. The cells were stored in liquid nitrogen, and expanded to passage 3 before  
50  
51 encapsulation.  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 hCCs encapsulation in gels: Cells were trypsinized and resuspended at  $15 \times 10^6$  cells/ml in the  
4 HA-TG solution, then the gelation was triggered as described previously. The gels were quickly  
5  
6 cast in 4 mm diameter UV-sterilized PDMS cylindrical molds (SYLGARD 184, Corning)  
7  
8 adhered to 10 mm coverslips. The gels were allowed to crosslink for 15 minutes at  $37^\circ\text{C}$  before  
9  
10 adding chondrogenic medium (DMEM (cat. 31966) supplemented with 10 ng/ml transforming  
11  
12 growth factor  $\beta 3$  (TGF- $\beta 3$ , Peprotech), 100 nM dexamethasone, 50  $\mu\text{g/ml}$  L-ascorbate-2-  
13  
14 phosphate, 40  $\mu\text{g/ml}$  proline, 1% penicillin-streptomycin, and 1% ITS+ Premix (Corning)). The  
15  
16 gels were incubated in a controlled humidified chamber ( $37^\circ\text{C}$ , 5% (vol/vol)  $\text{CO}_2$ ) for 3 weeks  
17  
18 and the culture media was replaced twice a week.  
19  
20  
21  
22  
23

24  
25 *Live imaging:* Gels were incubated for 1h in medium supplemented with 2  $\mu\text{M}$  calcein AM and  
26  
27 6.6  $\mu\text{g/ml}$  propidium iodide (PI), washed with fresh medium, and imaged on a Leica SP8  
28  
29 multiphoton microscope (25x water immersion objective, Mai Tai irradiation at 900 nm) with  
30  
31 simultaneous collection of second harmonic generation (SHG) and fluorescence. The pictures  
32  
33 presented were taken 60 to 70  $\mu\text{m}$  from the sample surface, as the signal deteriorated at deeper  
34  
35 depths.  
36  
37  
38

39  
40 *Immunohistochemistry:* Gels were fixed in 4% formaldehyde for 45 minutes, embedded in  
41  
42 O.C.T (Tissue-Tek O.C.T Compound Blue, Sysmex) and stored at  $-80^\circ\text{C}$ . 5  $\mu\text{m}$  thick sections  
43  
44 were cut using a Cryostat (CryoStar NX70, Thermo Scientific). Collagen 1 and 2 staining were  
45  
46 performed after 30 minutes of 0.2% (w/v) hyaluronidase digestion at  $37^\circ\text{C}$  and 1 hour blocking  
47  
48 with 5% BSA in PBS with 1:200 diluted mouse anti-collagen 1 (Abcam #ab6308) and 1:200  
49  
50 diluted rabbit anti-collagen 2 (Rockland 600-401-104). Proteoglycan staining was performed  
51  
52 after reducing the tissue with 10mM dithiothreitol in TBS pH 7.4 for 2 hours at  $37^\circ\text{C}$  and  
53  
54 alkylating with 40 mM iodoacetamide in PBS for 2 hours at  $37^\circ\text{C}$ . Sections were then digested  
55  
56  
57  
58  
59  
60

1  
2  
3 with 0.02 U/ml chondroitinase ABC for 40 minutes at 37°C and blocked for 1 hour at room  
4 temperature with 5% BSA before incubating with primary antibody (Hybridoma 12/21/1-C-6).  
5  
6 All primary antibodies were diluted in 1% (w/v) BSA in PBS and incubated overnight at 4°C.  
7  
8 Alexa Fluor 594 Goat Anti-Mouse IgG (Invitrogen, A11005), Alexa Fluor 488 Goat anti-rabbit  
9  
10 Alexa 488 (Invitrogen A11008) and Alexa Fluor 488 Goat anti-mouse (Invitrogen A11029)  
11  
12 secondary antibodies were used at 1:200 dilution in 1% BSA in PBS for 1 hour at RT. Finally,  
13  
14 slides were incubated for 10 minutes with the nuclear stain DAPI (Molecular Probes, Invitrogen)  
15  
16 before mounting with VectaMount AQ Mounting Medium (Vector Laboratories).  
17  
18  
19

20  
21  
22 *RNA extraction and PCR:* Samples were frozen in liquid nitrogen and crushed using pellet  
23  
24 pestles (Thomas Scientific). Total RNA was prepared using NucleoSpin miRNA kit (Macherey-  
25  
26 Nagel) and concentration was determined with a microplate reader Synergy H1 (BioTek  
27  
28 Instruments). RNA with an absorbance ratio at 260/280 nm between 1.9 and 2.1 was used for  
29  
30 PCR analysis. The Fast SYBR Green Master Mix (Applied Biosystems) was used to perform the  
31  
32 PCR amplification with 150 nM forward and reverse primer. All primers (see Table 1) were  
33  
34 designed across exon-exon junctions using Real Time PCR Design Tool from Integrated DNA  
35  
36 Technologies (<http://eu.idtdna.com/Scitools/Applications/RealTimePCR/Default.asp>) to avoid  
37  
38 the amplification of genomic DNA. All data came from 3 independent replicates and was  
39  
40 analyzed using the  $2^{-\Delta\Delta C_t}$  method<sup>31</sup> and normalized against the reference gene RPL13a<sup>32</sup> with  
41  
42 day 0 samples chosen as reference.  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52

53 **Table 1** Primer specification used for RT-PCR  
54  
55  
56  
57  
58  
59  
60



mRNA	Accession n°	BP		Primer sequence (5'-3')
<i>hRPL13a</i>	NM_012423	100	FWD	AAGTACCAGGCAGTGACAG
			REV	CCTGTTTCCGTAGCCTCATG
<i>hColl1a1</i>	NM_000088	83	FWD	CAGCCGCTTCACCTACAGC
			REV	TTTTGTATTCAATCACTGTCGCC
<i>hCol2a1</i>	NM_001844	92	FWD	GGAATTCGGTGTGGACATAGG
			REV	ACTTGGGTCCTTTGGGTTTG
<i>hCol10a1</i>	NM_000493	108	FWD	ATTCCTAGTGGCTCCAATGTG
			REV	GCCTACCTCCATATGCATTTT
<i>hACAN</i>	NM_001135.3	98	FWD	GAATGGGAACCAGCCTATAACC
			REV	TCTGTACTTTCCTCTGTTGCTG

### Acknowledgements

This work was supported by a CABMM startup grant, the ETH Zurich Foundation (Grant No. ETH-50 13-1), the Swiss National Science Foundation (Grant No. [CR3213\\_146338](#)) and FIFA/F-MARC (FIFA Medical Assessment and Research Center). We also acknowledge the help of the Scientific Center for Optical and Electron Microscopy (ScopeM) of ETH Zurich. The monoclonal antibody 12/21/1-C-6, developed by Caterson, B. was obtained from the Developmental Studies Hybridoma Bank, created by the NICHD of the NIH and maintained at The University of Iowa, Department of Biology, Iowa City, IA 52242.

### Supporting Information

Supplementary figures showing hCCs in MMP sensitive HA-TG as well as additional physical and chemical characterization of HA-TG available free of charge via the Internet at <http://pubs.acs.org>.

## References

1. (a) Becerra, J.; Andrades, J. A.; Guerado, E.; Zamora-Navas, P.; Lopez-Puertas, J. M.; Reddi, A. H., Articular cartilage: structure and regeneration. *Tissue Eng Part B Rev* **2010**, *16* (6), 617-27; (b) Makris, E. A.; Gomoll, A. H.; Malizos, K. N.; Hu, J. C.; Athanasiou, K. A., Repair and tissue engineering techniques for articular cartilage. *Nat Rev Rheumatol* **2015**, *11* (1), 21-34; (c) Ahmed, T. A.; Hincke, M. T., Strategies for articular cartilage lesion repair and functional restoration. *Tissue Eng Part B Rev* **2010**, *16* (3), 305-29.
2. (a) Basad, E.; Ishaque, B.; Bachmann, G.; Sturz, H.; Steinmeyer, J., Matrix-induced autologous chondrocyte implantation versus microfracture in the treatment of cartilage defects of the knee: a 2-year randomised study. *Knee Surg Sports Traumatol Arthrosc* **2010**, *18* (4), 519-27; (b) Saris, D.; Price, A.; Widuchowski, W.; Bertrand-Marchand, M.; Caron, J.; Drogset, J. O.; Emans, P.; Podskubka, A.; Tsuchida, A.; Kili, S.; Levine, D.; Brittberg, M.; group, S. s., Matrix-Applied Characterized Autologous Cultured Chondrocytes Versus Microfracture: Two-Year Follow-up of a Prospective Randomized Trial. *Am J Sports Med* **2014**, *42* (6), 1384-94.
3. Kon, E.; Filardo, G.; Di Martino, A.; Marcacci, M., ACI and MACI. *J Knee Surg* **2012**, *25* (1), 17-22.
4. (a) Albrecht, F. H., [Closure of joint cartilage defects using cartilage fragments and fibrin glue]. *Fortschr Med* **1983**, *101* (37), 1650-2; (b) Albrecht, F.; Roessner, A.; Zimmermann, E., Closure of osteochondral lesions using chondral fragments and fibrin adhesive. *Arch Orthop Trauma Surg* **1983**, *101* (3), 213-7.
5. (a) Cole, B. J.; Farr, J.; Winalski, C. S.; Hosea, T.; Richmond, J.; Mandelbaum, B.; De Deyne, P. G., Outcomes after a single-stage procedure for cell-based cartilage repair: a prospective clinical safety trial with 2-year follow-up. *Am J Sports Med* **2011**, *39* (6), 1170-9; (b) Farr, J.; Cole, B. J.; Sherman, S.; Karas, V., Particulated articular cartilage: CAIS and DeNovo NT. *J Knee Surg* **2012**, *25* (1), 23-9.
6. (a) Christensen, B. B.; Foldager, C. B.; Jensen, J.; Lind, M., Autologous Dual-Tissue Transplantation for Osteochondral Repair: Early Clinical and Radiological Results. *Cartilage* **2015**, *6* (3), 166-73; (b) Christensen, B. B.; Foldager, C. B.; Olesen, M. L.; Hede, K. C.; Lind, M., Implantation of Autologous Cartilage Chips Improves Cartilage Repair Tissue Quality in Osteochondral Defects: A Study in Gottingen Minipigs. *Am J Sports Med* **2016**.
7. Berdichevski, A.; Shachaf, Y.; Wechsler, R.; Seliktar, D., Protein composition alters in vivo resorption of PEG-based hydrogels as monitored by contrast-enhanced MRI. *Biomaterials* **2015**, *42*, 1-10.
8. (a) Stanish, W. D.; McCormack, R.; Forriol, F.; Mohtadi, N.; Pelet, S.; Desnoyers, J.; Restrepo, A.; Shive, M. S., Novel scaffold-based BST-CarGel treatment results in superior cartilage repair compared with microfracture in a randomized controlled trial. *J Bone Joint Surg Am* **2013**, *95* (18), 1640-50; (b) Shive, M. S.; Stanish, W. D.; McCormack, R.; Forriol, F.; Mohtadi, N.; Pelet, S.; Desnoyers, J.; Methot, S.; Vehik, K.; Restrepo, A., BST-CarGel(R)

1  
2  
3 Treatment Maintains Cartilage Repair Superiority over Microfracture at 5 Years in a Multicenter  
4 Randomized Controlled Trial. *Cartilage* **2015**, *6* (2), 62-72.

5  
6 9. Scholz, B.; Kinzelmann, C.; Benz, K.; Mollenhauer, J.; Wurst, H.; Schlosshauer, B.,  
7 Suppression of adverse angiogenesis in an albumin-based hydrogel for articular cartilage and  
8 intervertebral disc regeneration. *Eur Cell Mater* **2010**, *20*, 24-36; discussion 36-7.

9  
10 10. (a) Madeira, C.; Santhagunam, A.; Salgueiro, J. B.; Cabral, J. M., Advanced cell  
11 therapies for articular cartilage regeneration. *Trends Biotechnol* **2015**, *33* (1), 35-42; (b)  
12 Mardones, R.; Jofre, C. M.; Minguell, J. J., Cell Therapy and Tissue Engineering Approaches for  
13 Cartilage Repair and/or Regeneration. *Int J Stem Cells* **2015**, *8* (1), 48-53.

14  
15 11. Broguiere, N.; Isenmann, L.; Zenobi-Wong, M., Novel enzymatically cross-linked  
16 hyaluronan hydrogels support the formation of 3D neuronal networks. *Biomaterials* **2016**, *99*,  
17 47-55.

18  
19 12. (a) Hu, B. H.; Messersmith, P. B., Rational design of transglutaminase substrate peptides  
20 for rapid enzymatic formation of hydrogels. *J Am Chem Soc* **2003**, *125* (47), 14298-9; (b)  
21 Ehrbar, M.; Rizzi, S. C.; Schoenmakers, R. G.; Miguel, B. S.; Hubbell, J. A.; Weber, F. E.;  
22 Lutolf, M. P., Biomolecular hydrogels formed and degraded via site-specific enzymatic  
23 reactions. *Biomacromolecules* **2007**, *8* (10), 3000-7.

24  
25 13. Allison, D. D.; Grande-Allen, K. J., Review. Hyaluronan: a powerful tissue engineering  
26 tool. *Tissue Eng* **2006**, *12* (8), 2131-40.

27  
28 14. Masuko, K.; Murata, M.; Yudoh, K.; Kato, T.; Nakamura, H., Anti-inflammatory effects  
29 of hyaluronan in arthritis therapy: Not just for viscosity. *Int J Gen Med* **2009**, *2*, 77-81.

30  
31 15. Darwiche, S.; Scaletta, C.; Raffoul, W.; Pioletti, D. P.; Applegate, L. A., Epiphyseal  
32 Chondroprogenitors Provide a Stable Cell Source for Cartilage Cell Therapy. *Cell Med* **2012**, *4*  
33 (1), 23-32.

34  
35 16. Studer, D.; Cavalli, E.; Formica, F. A.; Kuhn, G. A.; Salzman, G.; Mumme, M.;  
36 Steinwachs, M. R.; Laurent-Applegate, L. A.; Maniura-Weber, K.; Zenobi-Wong, M., Human  
37 chondroprogenitors in alginate-collagen hybrid scaffolds produce stable cartilage in vivo.  
38 *Journal of tissue engineering and regenerative medicine* **2016**.

39  
40 17. Reynolds, T. C.; Butine, M. D.; Visich, J. E.; Gunewardena, K. A.; MacMahon, M.;  
41 Pederson, S.; Bishop, P. D.; Morton, K. M., Safety, pharmacokinetics, and immunogenicity of  
42 single-dose rFXIII administration to healthy volunteers. *Journal of thrombosis and haemostasis* :  
43 *JTH* **2005**, *3* (5), 922-8.

44  
45 18. (a) Pfeiler, E.; Toyoda, H.; Williams, M. D.; Nieman, R. A., Identification, structural  
46 analysis and function of hyaluronan in developing fish larvae (leptocephali). *Comparative*  
47 *biochemistry and physiology. Part B, Biochemistry & molecular biology* **2002**, *132* (2), 443-51;  
48 (b) Scott, J. E.; Heatley, F., Biological properties of hyaluronan in aqueous solution are  
49 controlled and sequestered by reversible tertiary structures, defined by NMR spectroscopy.  
50 *Biomacromolecules* **2002**, *3* (3), 547-53.

51  
52 19. Lutolf, M. P.; Hubbell, J. A., Synthesis and physicochemical characterization of end-  
53 linked poly(ethylene glycol)-co-peptide hydrogels formed by Michael-type addition.  
54 *Biomacromolecules* **2003**, *4* (3), 713-22.

55  
56 20. (a) Kim, M. K.; Choi, S. W.; Kim, S. R.; Oh, I. S.; Won, M. H., Autologous chondrocyte  
57 implantation in the knee using fibrin. *Knee Surg Sports Traumatol Arthrosc* **2010**, *18* (4), 528-  
58 34; (b) Patel, S.; Rodriguez-Merchan, E. C.; Haddad, F. S., The use of fibrin glue in surgery of  
59 the knee. *J Bone Joint Surg Br* **2010**, *92* (10), 1325-31.  
60

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
21. (a) Kuo, C. K.; Ma, P. X., Ionically crosslinked alginate hydrogels as scaffolds for tissue engineering: part 1. Structure, gelation rate and mechanical properties. *Biomaterials* **2001**, *22* (6), 511-21; (b) Drury, J. L.; Mooney, D. J., Hydrogels for tissue engineering: scaffold design variables and applications. *Biomaterials* **2003**, *24* (24), 4337-51.
  22. Adkisson, H. D.; Milliman, C.; Zhang, X.; Mauch, K.; Maziarz, R. T.; Streeter, P. R., Immune evasion by neocartilage-derived chondrocytes: Implications for biologic repair of joint articular cartilage. *Stem Cell Res* **2010**, *4* (1), 57-68.
  23. Cao, B.; Peng, R.; Li, Z.; Ding, J., Effects of spreading areas and aspect ratios of single cells on dedifferentiation of chondrocytes. *Biomaterials* **2014**, *35* (25), 6871-81.
  24. Park, S.; Hung, C. T.; Ateshian, G. A., Mechanical response of bovine articular cartilage under dynamic unconfined compression loading at physiological stress levels. *Osteoarthritis Cartilage* **2004**, *12* (1), 65-73.
  25. (a) Lee, F.; Chung, J. E.; Kurisawa, M., An injectable enzymatically crosslinked hyaluronic acid-tyramine hydrogel system with independent tuning of mechanical strength and gelation rate. *Soft Matter* **2008**, *4* (4), 880-887; (b) Jin, R.; Teixeira, L. S. M.; Dijkstra, P. J.; van Blitterswijk, C. A.; Karperien, M.; Feijen, J., Enzymatically-crosslinked injectable hydrogels based on biomimetic dextran-hyaluronic acid conjugates for cartilage tissue engineering. *Biomaterials* **2010**, *31* (11), 3103-3113; (c) Jin, R.; Teixeira, L. S. M.; Dijkstra, P. J.; van Blitterswijk, C. A.; Karperien, M.; Feijen, J., Chondrogenesis in injectable enzymatically crosslinked heparin/dextran hydrogels. *J Control Release* **2011**, *152* (1), 186-195.
  26. Chung, C.; Burdick, J. A., Influence of Three-Dimensional Hyaluronic Acid Microenvironments on Mesenchymal Stem Cell Chondrogenesis. *Tissue Eng Pt A* **2009**, *15* (2), 243-254.
  27. Burdick, J. A.; Prestwich, G. D., Hyaluronic Acid Hydrogels for Biomedical Applications. *Adv Mater* **2011**, *23* (12), H41-H56.
  28. Teixeira, L. S.; Feijen, J.; van Blitterswijk, C. A.; Dijkstra, P. J.; Karperien, M., Enzyme-catalyzed crosslinkable hydrogels: emerging strategies for tissue engineering. *Biomaterials* **2012**, *33* (5), 1281-90.
  29. Chen, F.; Yu, S. R.; Liu, B.; Ni, Y. Z.; Yu, C. Y.; Su, Y.; Zhu, X. Y.; Yu, X. W.; Zhou, Y. F.; Yan, D. Y., An Injectable Enzymatically Crosslinked Carboxymethylated Pullulan/Chondroitin Sulfate Hydrogel for Cartilage Tissue Engineering. *Sci Rep-Uk* **2016**, *6*.
  30. Lutolf, M. P.; Hubbell, J. A., Synthetic biomaterials as instructive extracellular microenvironments for morphogenesis in tissue engineering. *Nat Biotechnol* **2005**, *23* (1), 47-55.
  31. Matsiko, A.; Levingstone, T. J.; O'Brien, F. J.; Gleeson, J. P., Addition of hyaluronic acid improves cellular infiltration and promotes early-stage chondrogenesis in a collagen-based scaffold for cartilage tissue engineering. *J Mech Behav Biomed Mater* **2012**, *11*, 41-52.
  32. Studer, D.; Lischer, S.; Jochum, W.; Ehrbar, M.; Zenobi-Wong, M.; Maniura-Weber, K., Ribosomal protein l13a as a reference gene for human bone marrow-derived mesenchymal stromal cells during expansion, adipo-, chondro-, and osteogenesis. *Tissue Eng Part C Methods* **2012**, *18* (10), 761-71.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28

For Table of Contents Use Only

# Factor XIII Cross-linked Hyaluronan Hydrogels for Cartilage Tissue Engineering

*Nicolas Broguiere<sup>†1</sup>, Emma Cavalli<sup>†1</sup>, Gian M. Salzman<sup>2</sup>, Lee Ann Applegate<sup>3</sup>, Marcy Zenobi-  
Wong<sup>\*1</sup>*

29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

New hyaluronan-based hydrogels cross-linked with the transglutaminase factor XIII, together with human chondroprogenitor cells, are used for cartilage tissue engineering. The gels are injectable, adhere to cartilage, keep encapsulated cells highly viable, retain their shape and promote cell proliferation and chondrogenesis. Initially soft gels with cells reach a stiffness of the same order of magnitude as native cartilage after 3 weeks of culture.

